

Experimental evidence of effective $\langle 111 \rangle$ atomic exchanges in a B2 intermetallic alloy

Markus Stana*, Manuel Ross and Bogdan Sepiol

Universität Wien, Fakultät für Physik, Boltzmanngasse 5, 1090 Wien, Austria

June 23, 2016

We report on an atomic-scale X-ray Photon Correlation Spectroscopy study on Fe-rich FeAl in the B2-ordered regime revealing effective $\langle 111 \rangle$ -exchanges of atoms on the Al-sublattice. The diffusion mechanism responsible for these exchanges is the dominating process for chemical diffusion and therefore controls long-range material transport in the system. Comparison with previous atomistic results shows that the dominance of further exchanges can be characteristic at moderate temperatures where the system is highly ordered.

1 Introduction

It is one of the fundamental questions in the dynamics properties research to find the preferred paths of atomic motion on a lattice. Knowledge of such processes can, however, also be interesting for applied physics. Despite attractive properties like high specific strength, good corrosion and oxidation resistance and low material cost, the application of intermetallic compounds is still limited mainly by their high brittleness at low temperatures [Stol 94, Herr 03]. Knowing movement of single atoms can help in finding a way to tailor materials where such undesired characteristics would be spared.

It is clear that vacancies are the vehicles of diffusion in elementary metals, their solutions and alloys [Mehr 07]. While diffusion via a jump mechanism is well understood in solid solutions in frame of the encounter model [Eise 63, Wolf 80] and was recently investigated with the atomic-scale X-ray Photon Correlation Spectroscopy (aXPCS) [Stan 13], diffusion in intermetallic alloys is still subject of debate. The important boundary condition for diffusion in ordered intermetallics is the conservation of long-range order [Lidi 57]. Atomic exchanges of atoms belonging to different sublattices, e.g. nearest-neighbor jumps along a $\langle \frac{1}{2} \frac{1}{2} \frac{1}{2} \rangle$ -direction in case of a B2 ordered system are therefore suppressed. Effective jumps which lead to atomic exchanges farther than a nearest-neighbor position can not be described by a random movement of vacancies. The most established diffusion mechanisms conserving the order of the B2 phase and eventually leading to farther effective jumps are the Antistructure-Bridge Mechanism [Kao 93], the Triple-Defect Mechanism and the Huntington-McCombie-Elcock or 6-Jump Cycle [Hunt, Elco 58, Elco 59, Hunt 61] mechanism.

Even though it is not possible to directly follow the movement of the vacancy in an experiment, information about effective exchange vectors can shine light on the matter. Such effective jumps can either result from a direct exchange of an atom and a vacancy (e.g. direct $\langle 100 \rangle$ -jumps in a B2 system) or as changes in configuration before and after a sequence of correlated jumps like in the encounter model or the mechanisms mentioned above.

Fe-Al B2 ordered systems have been subject to plenty of diffusion studies (see e.g. Kao et al. [Kao 95]). For nearly stoichiometric FeAl as well as for a $\text{Fe}_{0.54}\text{Al}_{0.46}$ B2 system it was found that effective jumps are performed along $\langle 100 \rangle$ and $\langle 110 \rangle$ -directions with a ratio of $\langle 110 \rangle / \langle 100 \rangle$ of 2:1 with an

optional admixture of up to 10% of $\langle 111 \rangle$ -exchanges [Vogl 94, Feld 95]. These distribution could not be related directly to any specific diffusion mechanism. They could, however, be reproduced by Monte Carlo simulations [Wein 99]. One should notice that this was achieved assuming unreasonably high exchange energies between vacancies and atoms. The particular experimental result was that the dominant jump mechanism at elevated temperatures leads to an effective $\langle 110 \rangle$ -jump.

In this paper we report on the observation of chemical diffusion in $\text{Fe}_{0.54}\text{Al}_{0.46}$ at much lower temperatures where the degree of B2 order is considerably higher than in previous Quasielastic Mössbauer Spectroscopy (QMS) studies [Vogl 94, Feld 95]. Such an investigation was possible by using the new method of aXPCS [Leit 09]. This method is sensitive to chemical diffusion where atoms of different type exchange position in a coupled way depending on the short-range order in the system. This allows determining an effective diffusion coefficient which describes mutual influence of two or more alloy components. An effective jump is the exchange of two atoms of different type which in this particular case are iron and aluminum atoms. The aim of this experiment was to find out whether temperature and degree of long range order influence the probability distribution of effective jump vectors.

2 Theory

For a thorough introduction to the XPCS method see e.g. [Sutt 08, Leit 12, Stan 14]. Here we give only a very brief outline of the theory.

The intermediate scattering function $g^{(1)}(\vec{q}, \Delta t)$ is the Fourier transform of the Van Hove correlation function and therefore contains like the original function, complete information about atomic motion in space and in time.

The Siegert relation connects the intensity autocorrelation function, which is measured in an XPCS experiment and the amplitude correlation function, which is equivalent to the intermediate scattering function:

$$g^{(2)}(\vec{q}, \Delta t) = \frac{\langle I(\vec{q}, t) I(\vec{q}, t + \Delta t) \rangle_t}{\langle I(\vec{q}, t) \rangle_t^2} = 1 + \beta \left[g^{(1)}(\vec{q}, \Delta t) \right]^2 \quad (1)$$

Here, $\vec{q}$ is the scattering vector, $\langle \dots \rangle_t$ is the time-ensemble average and β is the contrast or Siegert factor [Shpy 14] and accounts for the coherent part of X-ray scattering.

In case of a discrete motion on a Bravais lattice the intensity autocorrelation function can be fitted as a simple

markus.stana@univie.ac.at

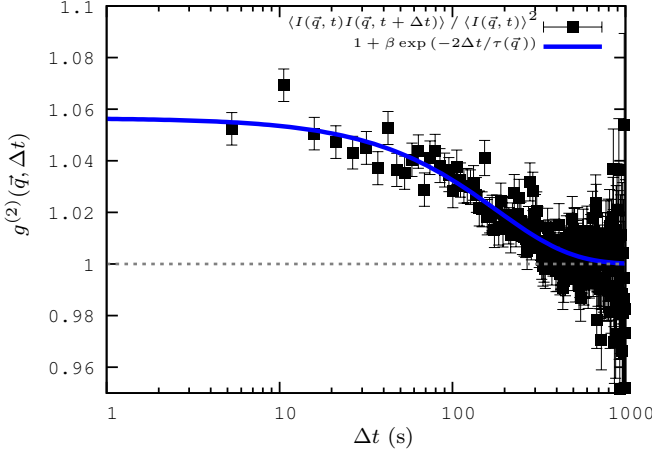


Figure 1: Intensity autocorrelation function measured at a scattering angle $2\Theta = 10^\circ$ and an azimuthal angle $\varphi = 2^\circ$. The fit according to (2) yields a correlation time of $\tau(\vec{q}) = 361(22)$ s and $\beta = 0.056(3)$.

exponential decay

$$g^{(2)}(\vec{q}, \Delta t) = 1 + \beta \exp \left[-2 \frac{\Delta t}{\tau(\vec{q})} \right]. \quad (2)$$

The correlation time $\tau(\vec{q})$ connects the measured data with the theoretical diffusion model in the following way:

$$\tau(\vec{q}) = \tau_0 \frac{I_{\text{SRO}}(\vec{q})}{\sum_n p_n \sum_{\Delta \vec{r}_{nj}} \left[1 - \exp(i\vec{q} \cdot \Delta \vec{r}_{nj}) \right]} \quad (3)$$

Here, τ_0 is the average residence time of an atom, p_n is the probability for an atom to end up at a particular neighboring position in the n -th neighboring shell after an exchange and $\Delta \vec{r}_{nj}$ is the vector that points to the j -th atom position in the n -th shell. The scaling term of short-range order intensity $I_{\text{SRO}}(\vec{q})$ accounts for De Gennes narrowing [De G 59] derived in this form for crystalline solids by Sinha and Ross [Sinh 88] and is necessary as aXPCS is a coherent method [Leit 11].

In ordered alloys with different sublattices σ , effective jumps between the sublattices can take place. In a B2 structure with two simple cubic sublattices σ^A and σ^B , the following effective jumps can occur: $\sigma^A \rightarrow \sigma^A$, $\sigma^A \rightarrow \sigma^B$, $\sigma^B \rightarrow \sigma^A$ and $\sigma^B \rightarrow \sigma^B$. For a B2 system, where the number of thermal defects is much smaller than the number of constitutional defects, it is possible that one sublattice is completely filled with the majority atoms, i.e. Fe (A -atoms). In this particular case the other sublattice σ^B is filled with the remaining excess atoms of type A and with B atoms. If so, chemical diffusion takes place only on the simple cubic Bravais lattice σ^B according to (3). This defect type with anti-structure atoms on one sublattice is often referred to as triple-defect system [Leit 15].

3 Experimental

The experiment was carried out at beamline P10 at the Petra III synchrotron source in Hamburg. The energy of the incident X-ray beam was chosen to be 7.05 keV in order to avoid iron fluorescence. The single crystalline sample was oriented with the $[111]$ -direction parallel to the beam. The parameterization of the $\vec{q}$ -vector by the scattering angle 2Θ and an azimuthal angle φ is given in the appendix. $\varphi = 0$ corresponds to the $[\bar{1}12]$ -direction.

A distance between sample and detector was 83 cm. A PIXIS-XB with a CCD array of 1340×1300 pixel of $20 \times 20 \mu\text{m}^2$ size was used. This camera had a readout time of

2.29 s/frame and an exposure time of 3 s was chosen. In order to monitor the stability of the setup and to check the equilibrium state of the sample, a two-time correlation function was calculated for each set of frames taken at a particular $\vec{q}$ -vector and measurements were repeated in arbitrary order for different $\vec{q}$ -vectors. A typical intensity autocorrelation function is shown in FIG. 1.

The single crystalline sample was purchased from Lamprecht, Germany (now MaTeCK) and was the same sample as used in a QMS study by Feldwisch et al. [Feld 95]. The composition was examined by EDX and was found to be to $c_{\text{Fe}} = 0.539(7)$ and $c_{\text{Al}} = 0.460(7)$. The lattice constant in $\text{Fe}_{0.54}\text{Al}_{0.46}$ is 2.929 Å at room temperature [Tayl 58].

4 Data evaluation

In order to evaluate the measured dataset with respect to (3), the short-range order intensity of the excessive iron atoms on the Al-sublattice has to be known. Unfortunately, information about short-range order in ordered alloys is very scarce in the literature and no information about the system at hand could be found. Attempts to experimentally determine the very weak diffuse scattering intensity were inconclusive. Therefore a simulation approach was chosen to determine the Warren-Cowley short-range order parameters [Cowl 60] for the Al-sublattice, which in turn can be used to calculate the corresponding short-range order intensity:

$$I_{\text{SRO}}(\vec{q}) = \sum_{n,j} \alpha_n^{\text{Al}} \cos(\vec{q} \cdot \Delta \vec{r}_{nj}) \quad (4)$$

The short-range order parameters are defined as $\alpha_n^{\text{Al}} = 1 - w_n^{\text{Al}}/c^{\text{Al}}$, where w_n^{Al} is, starting from a Fe atom on the Al-sublattice, the probability to find an Al atom in the n th neighboring shell within the Al-sublattice and c^{Al} is the overall concentration of Al atoms on the Al-sublattice.

Simulations were carried out using an off-lattice Monte-Carlo approach [Bert 07]. The potentials used were taken from an embedded atom method study by Ouyang et al. [Ouya 12]. This potential reproduces successfully numerous

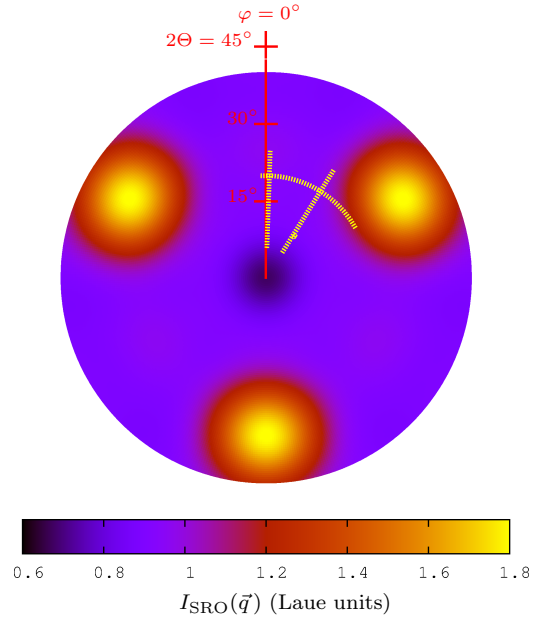


Figure 2: A map of short-range order intensity calculated according to (4) for a sample oriented in $[111]$ -direction from Warren-Cowley parameters as given in TAB. 1. The yellow lines represent the regions of reciprocal space where aXPCS measurements were carried out (cf. FIG. 4). The azimuthal angle is chosen such that $\varphi = 0$ corresponds to $[\bar{1}12]$ -direction.

n	1	2	3	4
lmn	100	110	111	200
$\alpha_n^{\text{Al}} \times 10^{-2}$	-6.15(4)	2.33(6)	-1.45(5)	0.16(6)
n	5	6	7	8
lmn	210	211	220	221
$\alpha_n^{\text{Al}} \times 10^{-2}$	-0.44(3)	-0.08(4)	-0.36(5)	0.00(4)

Table 1: Warren-Cowley parameters calculated using an off-lattice Monte Carlo approach [Stan 16] for neighbor shells (n) within the cubic Al-sublattice in B2 ordered $\text{Fe}_{0.54}\text{Al}_{0.46}$. Components of vectors to a particular neighbor shell in unit of a are given by lmn .

properties of the Fe–Al system, like phonon dispersion spectra and elastic constants. For a temperature of $0.42 \times T_m$ a vacancy concentration of 0.2% was used due to experiment [Koga 97, Hehe 01]. For a detailed discussion of the simulation procedure see [Stan 16]. With these potentials a lattice constant of $a = 2.98 \text{ \AA}$ was simulated, which is in reasonable agreement with experimental data [Tayl 58]. The Warren-Cowley parameters found with this approach are given in TAB. 1.

5 Results

5.1 Determination of effective jumps

Previous QMS measurements yielded distributions of effective jump vectors for self diffusion in a near stoichiometric B2 system of 35 % of $\langle 100 \rangle$ -jumps and 65 % of $\langle 110 \rangle$ -jumps or alternatively 26 % of $\langle 100 \rangle$ -jumps, 64 % of $\langle 110 \rangle$ -jumps and 10 % of $\langle 111 \rangle$ -jumps at 1338 K [Vogl 94]. The same technique was used for studying an off-stoichiometric nominal composition of $\text{Fe}_{0.55}\text{Al}_{0.45}$ [Feld 95]. An effective jump vector distribution of 30 % of $\langle 100 \rangle$ -jumps, 50 % of $\langle 110 \rangle$ -jumps and 20 % of $\langle 111 \rangle$ -jumps was found at a temperature of 1363 K, which corresponds to a homologous temperature of $0.87 \times T_m$.

Here we present an aXPCS measurement carried out at 653 K, which corresponds to a homologous temperature of only $0.42 \times T_m$. Intensity autocorrelation functions were recorded for different pairs of $(2\Theta, \varphi)$. Two models were tested against the correlation times gained according to (2). The first model implicated a combination of $\langle 100 \rangle$ and of $\langle 110 \rangle$ -exchanges, that is a combination of nearest-neighbor and next-nearest neighbor effective exchanges within the simple cubic Al-sublattice. For the second model, $\langle 111 \rangle$ -exchanges were additionally included. All experimentally determined correlation functions of the datasets for points in reciprocal space parameterized by 2Θ and φ were fitted simultaneously. The free parameter of this fit according to (3) were the average residence time τ_0 and a contrast $\beta(2\Theta, \varphi)$ for each pair of adjustable measurement parameters.



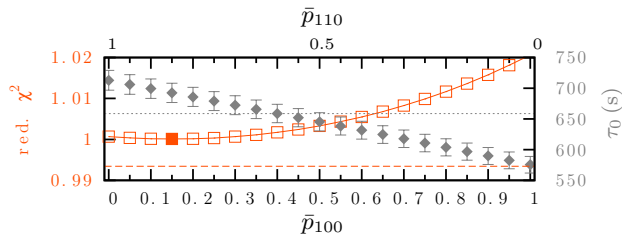


Figure 3: Variance of residuals and average residence time (τ_0) from fitting all measured intensity correlation functions simultaneously with a model consisting of $\langle 100 \rangle$ and $\langle 110 \rangle$ -exchanges. The best fit was found for 15% $\langle 100 \rangle$ -exchanges. The broken line represents the variance of residuals and the dotted line τ_0 for a model with 36% $\langle 100 \rangle$, 12% $\langle 110 \rangle$ and 52% $\langle 111 \rangle$ -exchanges.

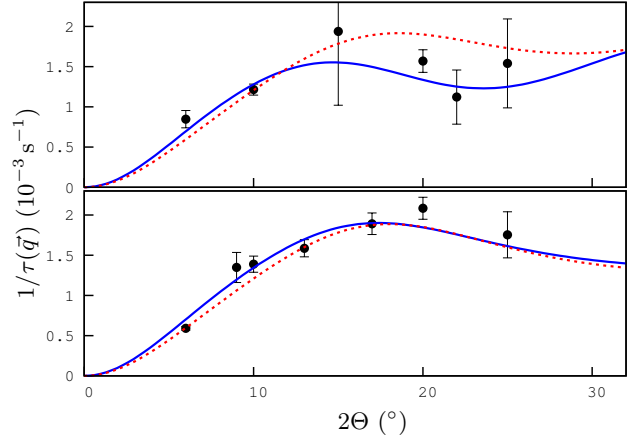

(a) Inverse of correlation time $\tau(\vec{q})$ as yielded by a fit of intensity-correlation functions at different scattering angles 2Θ for $\varphi = 2^\circ$ (bottom) and $\varphi = 32^\circ$ (top).

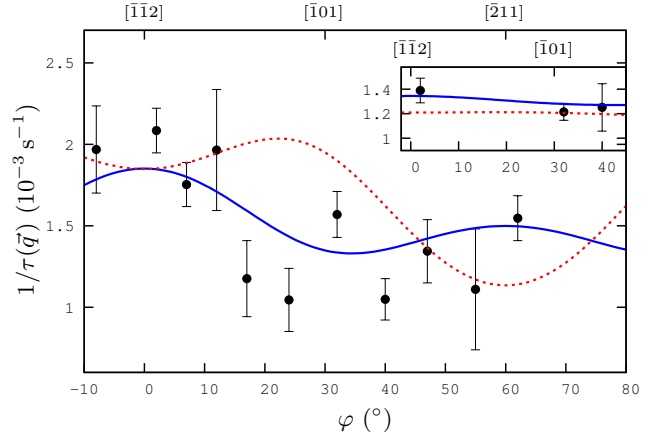

(b) Inverse of correlation time $\tau(\vec{q})$ yielded by a fit of intensity-correlation functions at different azimuthal angles φ for $2\Theta = 20^\circ$ and $2\Theta = 10^\circ$ (insert).

Figure 4: Diffusion models compared with aXPCS measurements. The black symbols with error bars represent the inverse of the correlation times for different positions in reciprocal space. The full, blue line represents a model including 36% $\langle 100 \rangle$, 12% $\langle 110 \rangle$ and 52% $\langle 111 \rangle$ -exchanges. The broken, red line represents a model with 15% $\langle 100 \rangle$ and 85% $\langle 110 \rangle$ -exchanges.

Results of this procedure are shown in FIG. 3. For the first model composed of $\bar{p}_{100}$ $\langle 100 \rangle$ -exchanges and of $\bar{p}_{110} = 1 - \bar{p}_{100}$ $\langle 110 \rangle$ -exchanges it can clearly be seen, that $\bar{p}_{110} > \bar{p}_{100}$. The best fit was found for 15% $\langle 100 \rangle$ and 85% $\langle 110 \rangle$ -exchanges. It can also be seen that introducing the possibility of $\langle 111 \rangle$ -exchanges yields an improved agreement of model 2 with the experimental data. The best fit for this model was gained combining 36% $\langle 100 \rangle$, 12% $\langle 110 \rangle$ and 52% of $\langle 111 \rangle$ -exchanges.

The fact that $\langle 111 \rangle$ -exchanges are needed to reproduce the measured data can also be seen when visually comparing both models, each with best fitting parameter, with individually fitted correlation times $\tau(\vec{q})$ for each point in reciprocal space where measurements were taken. This is shown in (3).

It shall be noted, that when neglecting short-range order ($I_{\text{SRO}}(\vec{q}) = 1$) a model including 50% $\langle 111 \rangle$ -exchanges still agrees better with the experimental data than one exclusively including of $\langle 100 \rangle$ and $\langle 110 \rangle$ -exchanges.

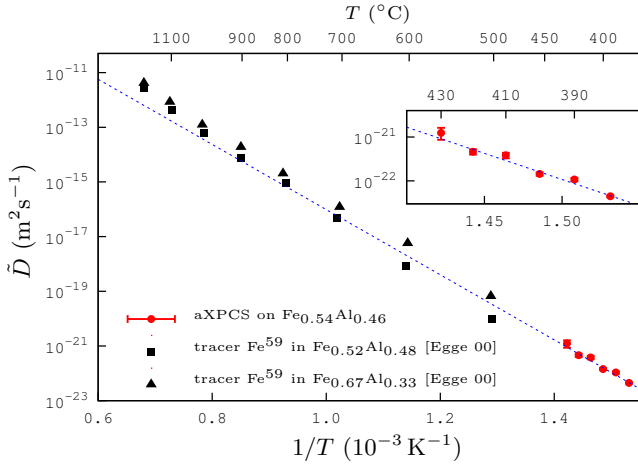


Figure 5: Temperature dependence of chemical diffusivities $\tilde{D}$ calculated from aXPCS data using the model including $\langle 111 \rangle$ -exchanges. For comparison, data from tracer measurements [Egge 00] in similar compositions is also shown. The blue line represents a fit to the aXPCS data according to the Arrhenius law as shown in (6).

5.2 Temperature dependence

Chemical diffusivities can be calculated from measurements at a certain $\vec{q}$ -vector for different temperatures using the Einstein-Smoluchowski relation:

$$\tilde{D}(T) = \frac{\langle R^2 \rangle}{6\tau_0} = \frac{\sum_n \bar{p}_n |r_n|^2}{6\tau_0}, \quad (5)$$

with $\bar{p}_n = p_n Z_n$ and Z_n the coordination number.

Chemical diffusivities found at different temperatures are shown in FIG. 5 in comparison to self diffusion data found by tracer measurements [Egge 00].

The data measured in this study can be used to find the activation energy ($\tilde{E}_a$) of chemical diffusion by means of the Arrhenius equation:

$$\tilde{D}(T) = \tilde{D}_0 \exp\left(-\frac{\tilde{E}_a}{k_B T}\right), \quad (6)$$

where k_B is the Boltzmann constant. The second model with jump probabilities $\bar{p}_{100} = 0.36$, $\bar{p}_{110} = 0.12$ and $\bar{p}_{111} = 0.52$ was applied, yielding a value of $\tilde{E}_a = 2.4(2)$ eV, which is in good agreement with the activation energy as a sum of formation and migration enthalpy of $E_a = 2.5(3)$ eV found by time-differential length change measurements for $\text{Fe}_{0.55}\text{Al}_{0.45}$ [Scha 99].

6 Discussion

It was shown that the dominating diffusion mechanism in B2 $\text{Fe}_{0.54}\text{Al}_{0.46}$ leads to effective $\langle 111 \rangle$ -exchanges. A sequence of six correlated jumps of a vacancy, which is known in three different variations in a B2 ordered system, can lead to effective $\langle 100 \rangle$ -jumps (there are two possibilities, a bent and a straight form) or to effective $\langle 110 \rangle$ -jumps. If an anti-structure atom is involved in the process this mechanism would lead to a corresponding exchange of two atoms of different kind along one of these two jump vectors. The six-jump cycle can therefore be ruled out as the dominating mechanism in this system at low homologous temperatures. In order to make an effective $\langle 111 \rangle$ -jump possible, at least ten correlated jumps of one vacancy are required. As it is very unlikely that the energy landscape favors ten over six correlated jumps, mechanisms of this kind can be categorically ruled out as the dominating process of chemical diffusion in this system.

The anti-structure bridge mechanism is a percolation dependent mechanism. A closed net of nearest-neighbor atoms of the majority type is necessary to allow for nearest-neighbor exchanges of vacancies with majority atoms which does, however, not lead to chemical diffusion. The percolation threshold for B2 ordered systems was found to be 54.9(2) at.% [Divi 97]. The composition under investigation here, therefore, lies just a little below this threshold. It is rather surprising that chemical diffusivities are similar to the self-diffusion of iron measured by a tracer method [Egge 00]. This can be seen as an important argument that the system is not fully percolated and the gaps between the percolated areas are bottlenecks for long-range diffusion.

It can be assumed that the anti-structure bridge mechanism takes place in isolated regions, where the self diffusion constant would accordingly be much higher than the measured chemical diffusivity. In order to allow for material transport beyond the borders of the isolated, percolated clusters a mechanism bridging the gaps between these regions must take place.

One possible explanation for such a mechanism would be the formation of a linear triple defect at the rim of a percolated cluster, where two vacancies with an anti-structure Fe-antisite atom in their middle along $\langle 111 \rangle$ -direction exists. This defect could then diffuse by exchange its position with an Al-atom, leading to a transport of one Fe-atom from one percolated cluster to another. Extensive ab initio simulations are necessary to assess this hypothesis.

7 Conclusions

We could show that aXPCS is capable of determining effective atomic exchanges and chemical diffusivities at temperatures inaccessible to other methods of diffusion studies with atomistic resolution. It was thus possible to study atomistic diffusion processes in a well ordered intermetallic for the first time. In the non-stoichiometric long-range ordered $\text{Fe}_{0.54}\text{Al}_{0.46}$ system at $0.42 \times T_m$ the dominating vacancy diffusion mechanism leads to effective $\langle 111 \rangle$ -exchanges of Fe and Al atoms. The activation energy of chemical diffusion was found to be 2.4(2) eV.

Acknowledgements

This research was funded by the Austrian Science Fund (FWF) contracts P-22402 and P-28232.

We thank S. Puchegger from Faculty Center for Nano Structure Research University of Vienna for the EDX analysis. We also thank M. Sprung and F. Westermeyer from beamline P10, PETRA III in Hamburg for a comprehensive support during our beamtimes.

Special thanks go to our collaborator Michael Leitner, now at Technische Universität München, Physik-Department E13, for many discussions and help in evaluating XPCS data.

Appendix

The parameterization of the reciprocal space vector for elastic scattering and a sample oriented such that the (111) plane is perpendicular to the X-ray beam, $[111] \parallel \vec{k}_{\text{in}}$, with $k_0 = |\vec{k}_{\text{in}}|$ and $\hat{x}, \hat{y}, \hat{z}$ the Cartesian coordinates, is given by:

$$\begin{aligned} \vec{q}(2\Theta, \varphi) = & 2k_0 \sin\left(\frac{2\Theta}{2}\right) \times \left(\frac{\sin(2\Theta/2)}{\sqrt{3}} - \frac{\cos(2\Theta/2)}{6} \left(\sqrt{6} \cos(\varphi) + 3\sqrt{2} \sin(\varphi) \right) \hat{x} \right. \\ & \left. + \left(\frac{\sin(2\Theta/2)}{\sqrt{3}} + \frac{\cos(2\Theta/2)}{6} \left(-\sqrt{6} \cos(\varphi) + 3\sqrt{2} \sin(\varphi) \right) \right) \hat{y} + \frac{\sqrt{2} \cos(2\Theta/2) \cos(\varphi) + \sin(2\Theta/2)}{\sqrt{3}} \hat{z} \right) \end{aligned} \quad (7)$$

References

- [Bert 07] L. Berthier and W. Kob. “The Monte Carlo dynamics of a binary Lennard-Jones glass-forming mixture”. *J. Phys.: Condens. Matter*, Vol. 19, No. 20, p. 205130, Apr 2007. 10.1088/0953-8984/19/20/205130.
- [Cowl 60] J. Cowley. “Short- and Long-Range Order Parameters in Disordered Solid Solutions”. *Phys. Rev.*, Vol. 120, No. 5, pp. 1648–1657, Dec 1960. 10.1103/physrev.120.1648.
- [De G 59] P. De Gennes. “Liquid dynamics and inelastic scattering of neutrons”. *Physica*, Vol. 25, No. 7-12, pp. 825–839, Jan 1959. 10.1016/0031-8914(59)90006-0.
- [Divi 97] S. V. Divinski and L. N. Larikov. “Diffusion by anti-structure defects in non-stoichiometric intermetallic compounds with B2 and structures”. *J. Phys.: Condens. Matter*, Vol. 9, No. 37, pp. 7873–7883, Sep 1997. 10.1088/0953-8984/9/37/018.
- [Egge 00] M. Eggersmann and H. Mehrer. “Diffusion in intermetallic phases of the Fe-Al system”. *Philosophical Magazine A*, Vol. 80, No. 5, p. 12191244, May 2000. 10.1080/01418610008212112.
- [Eise 63] M. Eisenstadt and A. G. Redfield. “Nuclear Spin Relaxation by Translational Diffusion in Solids”. *Physical Review*, Vol. 132, No. 2, p. 635643, Oct 1963. 10.1103/physrev.132.635.
- [Elco 58] E. W. Elcock and C. W. McCombie. “Vacancy Diffusion in Binary Ordered Alloys”. *Phys. Rev.*, Vol. 109, pp. 605–606, Jan 1958. 10.1103/PhysRev.109.605.
- [Elco 59] E. W. Elcock. “Vacancy Diffusion in Ordered Alloys”. *Proceedings of the Physical Society*, Vol. 73, No. 2, p. 250264, Feb 1959. 10.1088/0370-1328/73/2/314.
- [Feld 95] R. Feldwisch, B. Sepiol, and G. Vogl. “Elementary diffusion jump of iron atoms in intermetallic phases studied by Mössbauer spectroscopy – II. From order to disorder”. *Acta Metallurgica et Materialia*, Vol. 43, No. 5, p. 20332039, May 1995. 10.1016/0956-7151(94)00382-r.
- [Hehe 01] T. Hehenkamp, P. Scholz, B. Köhler, and R. Kerl. “Vacancy Formation and Diffusion in FeAl-Alloys”. *Defect and Diffusion Forum*, Vol. 194-199, pp. 389–396, 2001. 10.4028/www.scientific.net/ddf.194-199.389.
- [Herr 03] J. Herrmann, G. Inden, and G. Sauthoff. “Deformation behaviour of iron-rich iron-aluminum alloys at low temperatures”. *Acta Materialia*, Vol. 51, No. 10, pp. 2847–2857, Jun 2003. 10.1016/s1359-6454(03)00089-2.
- [Hunt] H. B. Huntington. private communication to Dr. Slifkin.
- [Hunt 61] H. Huntington, N. Miller, and V. Nerses. “Self-diffusion in 50-50 Gold-Cadmium”. *Acta Metallurgica*, Vol. 9, No. 8, p. 749754, Aug 1961. 10.1016/0001-6160(61)90105-5.
- [Kao 93] C. Kao and Y. Chang. “On the composition dependencies of self-diffusion coefficients in B2 intermetallic compounds”. *Intermetallics*, Vol. 1, No. 4, p. 237250, Jan 1993. 10.1016/0966-9795(93)90035-t.
- [Kao 95] C. Kao, S. Kim, and Y. Chang. “Diffusional behavior in B2 intermetallic compounds”. *Materials Science and Engineering: A*, Vol. 192-193, p. 965979, Feb 1995. 10.1016/0921-5093(95)03344-0.
- [Koga 97] M. Kogachi and T. Haraguchi. “Quenched-in vacancies in B2-structured intermetallic compound FeAl”. *Materials Science and Engineering: A*, Vol. 230, No. 1-2, pp. 124–131, Jul 1997. 10.1016/s0921-5093(97)00016-6.
- [Leit 09] M. Leitner, B. Sepiol, L.-M. Stadler, B. Pfau, and G. Vogl. “Atomic diffusion studied with coherent X-rays”. *Nat Mater*, Vol. 8, No. 9, pp. 717–720, Jul 2009. 10.1038/nmat2506.
- [Leit 11] M. Leitner and G. Vogl. “Quasi-elastic scattering under short-range order: the linear regime and beyond”. *J. Phys.: Condens. Matter*, Vol. 23, No. 25, p. 254206, Jun 2011. 10.1088/0953-8984/23/25/254206.
- [Leit 12] M. Leitner. *Studying Atomic Dynamics with Coherent X-rays*. Springer Berlin Heidelberg, 2012. 10.1007/978-3-642-24121-5.
- [Leit 15] M. Leitner. “Thermodynamics of point defects and diffusion mechanisms in B2-ordered compounds”. 2015. arXiv:1503.03798.
- [Lidi 57] A. Lidiard. “Vacancy Diffusion Mechanism in Ordered Alloys”. *Physical Review*, Vol. 106, No. 4, p. 823, 1957. 10.1103/PhysRev.106.823.
- [Mehr 07] H. Mehrer. *Diffusion in Solids*. Springer Berlin Heidelberg, 2007. 10.1007/978-3-540-71488-0.
- [Ouya 12] Y. Ouyang, X. Tong, C. Li, H. Chen, X. Tao, T. Hickel, and Y. Du. “Thermodynamic and physical properties of FeAl and Fe₃Al: an atomistic study by EAM simulation”. *Physica B: Condensed Matter*, Vol. 407, No. 23, pp. 4530–4536, Dec 2012. 10.1016/j.physb.2012.08.025.
- [Scha 99] H.-E. Schaefer, K. Frenner, and R. Würschum. “Time-Differential Length Change Measurements for Thermal Defect Investigations: Intermetallic B2-FeAl and B2-NiAl Compounds, a Case

- Study". *Physical Review Letters*, Vol. 82, No. 5, pp. 948–951, Feb 1999. 10.1103/physrevlett.82.948.
- [Shpy 14] O. G. Shpyrko. "X-ray photon correlation spectroscopy". *J Synchrotron Rad*, Vol. 21, No. 5, pp. 1057–1064, Aug 2014. 10.1107/s1600577514018232.
- [Sinh 88] S. Sinha and D. Ross. "Self-consistent density response function method for dynamics of light interstitials in crystals". *Physica B+ C*, Vol. 149, No. 1, pp. 51–56, 1988. 10.1016/0378-4363(88)90218-5.
- [Stan 13] M. Stana, M. Leitner, M. Ross, and B. Sepiol. "Studies of atomic diffusion in Ni–Pt solid solution by x-ray photon correlation spectroscopy". *J. Phys.: Condens. Matter*, Vol. 25, No. 6, p. 065401, Jan 2013. 10.1088/0953-8984/25/6/065401.
- [Stan 14] M. Stana, M. Ross, and B. Sepiol. "Atomic Migration Studies with X-Ray Photon Correlation Spectroscopy". *Diffusion Foundations*, Vol. 2, p. 7394, Sep 2014. 10.4028/www.scientific.net/df.2.73.
- [Stan 16] M. Stana, B. Sepiol, M. Leitner, and R. Kozubski. "Chemical ordering beyond the superstructure in long-range ordered systems". *to be published*, 2016.
- [Stol 94] N. Stoloff and C. Liu. "Environmental embrittlement of iron aluminides". *Intermetallics*, Vol. 2, No. 2, pp. 75–87, Jan 1994. 10.1016/0966-9795(94)90001-9.
- [Sutt 08] M. Sutton. "A review of X-ray intensity fluctuation spectroscopy". *Comptes Rendus Physique*, Vol. 9, No. 5-6, p. 657667, Jun 2008. 10.1016/j.crhy.2007.04.008.
- [Tayl 58] A. Taylor and R. Jones. "Constitution and magnetic properties of iron-rich iron-aluminum alloys". *Journal of Physics and Chemistry of Solids*, Vol. 6, No. 1, p. 1637, Jul 1958. 10.1016/0022-3697(58)90213-0.
- [Vogl 94] G. Vogl and B. Sepiol. "Elementary diffusion jump of iron atoms in intermetallic phases studied by Mossbauer spectroscopy—I. Fe-Al close to equiatomic stoichiometry". *Acta Metallurgica et Materialia*, Vol. 42, No. 9, p. 31753181, Sep 1994. 10.1016/0956-7151(94)90416-2.
- [Wein 99] R. Weinkamer, P. Fratzl, B. Sepiol, and G. Vogl. "Monte Carlo simulations of Mössbauer spectra in diffusion investigations". *Physical Review B*, Vol. 59, No. 13, p. 8622, 1999. 10.1103/PhysRevB.59.8622.
- [Wolf 80] D. Wolf. "Diffusion and correlation effects in nonstoichiometric crystals". *Journal of Physics and Chemistry of Solids*, Vol. 41, No. 10, pp. 1053–1063, 1980. 10.1016/0022-3697(80)90059-1.